

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead[®]

sales@rautomead.com
www.rautomead.com

Description

This process and plant described is intended to produce semi-finished brass rods and sections at an net output rate of up to around 150 tonnes per month, using either virgin metals or scrap brass feedstock.

The plant is designed for production of bars up to 4m long; 15mm - 45mm diameter and hexagon sections 15mm - 40mm across flats.

It is assumed that feedstock comprises 100% brass scrap, including in-house scrap arisings in the form of machining swarf and bar ends and reject machined components or forgings. Bought-in scrap of a similar nature to a known composition can also be used. Minor additions of virgin zinc and lead are added as required.

Process Route

- 1) **Feedstock preparation**, storage and feeding to melting furnace.
- 2) **Induction melting** of feedstock using a 1000Kg capacity 400 Kg/hr maximum coreless steel shell melting furnace.
- 3) **Metal transfer** via a refractory lined heated (normally by gas fired burners) launder.
- 4) **Continuous casting** of two strands of rod by a Rautomead RT850 Horizontal Continuous Casting Machine.
- 5) **Cut to length** (typically 3m - 4m) using a hand held powered bandsaw.
- 6) **Rod pointing** to reduce diameter of bar at one end to allow feed into shaving bench.
- 7) **Hydraulic shaving**, shaving straight lengths up to 4m long, removing up to a maximum depth of 1mm using a hydraulic shave bench with 3 shave dies..
- 8) **De-Tagging saw** to remove pointed end and cut to length.
- 9) **Bar straightening** using a 2 roll bar straightener.
- 10) **Storage and racking**.
- 11) **Quality control & testing**.

A typical factory layout demonstrating the equipment layout to achieve above process route is shown in drawing RD5147-4 attached at appendix C.

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead

sales@rautomead.com

www.rautomead.com

Equipment

1. Feedstock Preparation, Storage and Feeding to Melting Furnace

Scrap from manufacturing processes such as reject components, swarf and bar ends where the composition is known is ideally suited to this process. This requires to be reasonably clean, dry and free from oil. Excessive amounts of cutting lubricant result in high levels of gaseous emissions. The subsequent weight loss also contributes to a net reduction in yield.

Solid reject components from in house manufacturing process are usually relatively clean and dry and do not require special cleaning or drying. Storage is normally in bins or hoppers, which can be lifted directly onto the melting furnace platform.

Swarf and bar ends require to be dried by centrifuging. Storage can again be in bins or hoppers but a feature of swarf is that it can be transported, by conveyor, to the furnace and fed directly, using a vibratory table. In this case any sold scrap can be added manually to the vibratory table as the swarf/bar ends are charged. This approach is particularly recommended where the cost of labour is high.



Fig. 1 Swarf Drying Equipment

Bought in scrap should be treated with caution. Quality scrap to the correct composition may be available from known sources, whereas trade scrap from unknown sources often contains ferrous and other impurities, making it unsuitable.

A swarf drying and handling system can be tailored to suit a particular installation but a basic system would typically consist of: -

- a) A screw conveyor fed by tipper bins which raise the swarf/bar end mixture to a bar end separator. The bar ends and any random components are separated from the swarf and fed directly to a separate output storage hopper. This is loaded directly onto the melting furnace platform by crane or forklift truck.
- b) The swarf is fed to a centrifuge, which separates the soluble oil, producing dry swarf of approximately 1-2% W/W soluble oil content. The oil is stored in a collection tank.

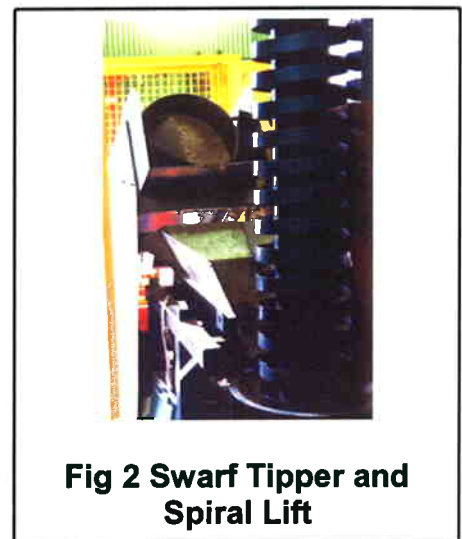


Fig 2 Swarf Tipper and Spiral Lift

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead[®]

sales@rautomead.com
www.rautomead.com

- c) The hopper of dried swarf is moved by fork lift to a swarf elevating and feeding system, where it is tipped into the feed of a spiral elevator. As the swarf bar ends exit the spiral elevator, the material passes through a rotary self-cleaning magnetic separator to extract any contaminating ferrous materials.



Fig 3 Spiral Lift Exit feeding Rotary Magnetic Separator



Fig 4 Vibrating Table feeding Swarf into Furnace

- d) The swarf is then fed in a controlled fashion into the furnace using an 80 m³/hr vibratory hopper feeder (rate controlled by the operator). At this stage the bar ends and any solid scrap are added manually.

If a conveyor/vibrating feed table is not used, then there are two other basic approaches to the storage and feeding of the scrap to the furnace.

- i. The scrap may be stored remotely from the furnace. The charges are weighed into specially designed feed hoppers, which are transported to the furnace by overhead crane to be fed directly into the furnace.



Fig 5 Feed Hooper for use with Overhead Crane



Fig 6 Storage Hoppers and weighing Station of Furnace Platform

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead

sales@rautomead.com
www.rautomead.com

II. Buffer stores of swarf/bar ends and solid scrap hoppers may be located on the furnace platform along with buckets and weighing scales. Operators charge the materials into buckets by shovel for feeding into the furnace. This is labour intensive, but avoids the need for an overhead crane. The hoppers are loaded onto the platform by forklift truck.

Regardless of the feeding method employed, a stock of virgin zinc and lead along with weighing scales must be located on the melting furnace platform. Some manual assistance, using a "puddling" pole, may be required to ensure the charge is pushed through the surface of the melt.

2. Induction Melting

350 kW, 1000Kg capacity, medium frequency coreless steel shell melting furnace with hydraulically operated trunion tilted fume hood and hydraulic integral lid.

The furnace includes hydraulic power pack, load cell weighing system with digital readout, computerised melt manager and a recirculating closed circuit water cooling system.



Fig 7 Induction Premelting and RT850 Installation

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead[®]

sales@rautomead.com
www.rautomead.com

The melting furnace is designed to pour batches of 400Kg in a 60minute period leaving a heel of 600Kg in the crucible to facilitate the melting and alloying of each succeeding batch. This would allow for sufficient time to perform the following cycle:

- 1) Pour 400Kg into the RT850 continuous casting furnace,
- 2) De-slag the surface including scraping the side walls,
- 3) Charge new material into the premelting furnace.
- 4) Sample molten metal.
- 5) Prepare sample on lathe and analyse with the spectrometer.
- 6) Adjust the chemistry of the molten brass and repeat analysis
- 7) Repeat steps 5), 6), and 7) as required.
- 8) Check and adjust molten metal temperature.

3. Metal Transfer

The closed and heated metal transfer launder is provided to transfer liquid metal from the melting furnace to the RT850 continuous casting machine crucible. The launder consists of a steel shell fabrication lined with a suitable refractory. The launder is heated, typically using gas fired burners.



Fig 8 Brass being transferred to Rautomead Casting Machine


The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead

sales@rautomead.com
www.rautomead.com

4. Continuous Casting

A 105 kVA resistance heated furnace designed to cast two strands of brass bar in sizes ranging from 15mm to 45mm diameter. The technology is based around a graphite crucible to contain the brass, graphite resistance heating elements and graphite dies cooled with copper coolers. Crucible capacity is approx. 750 kg.

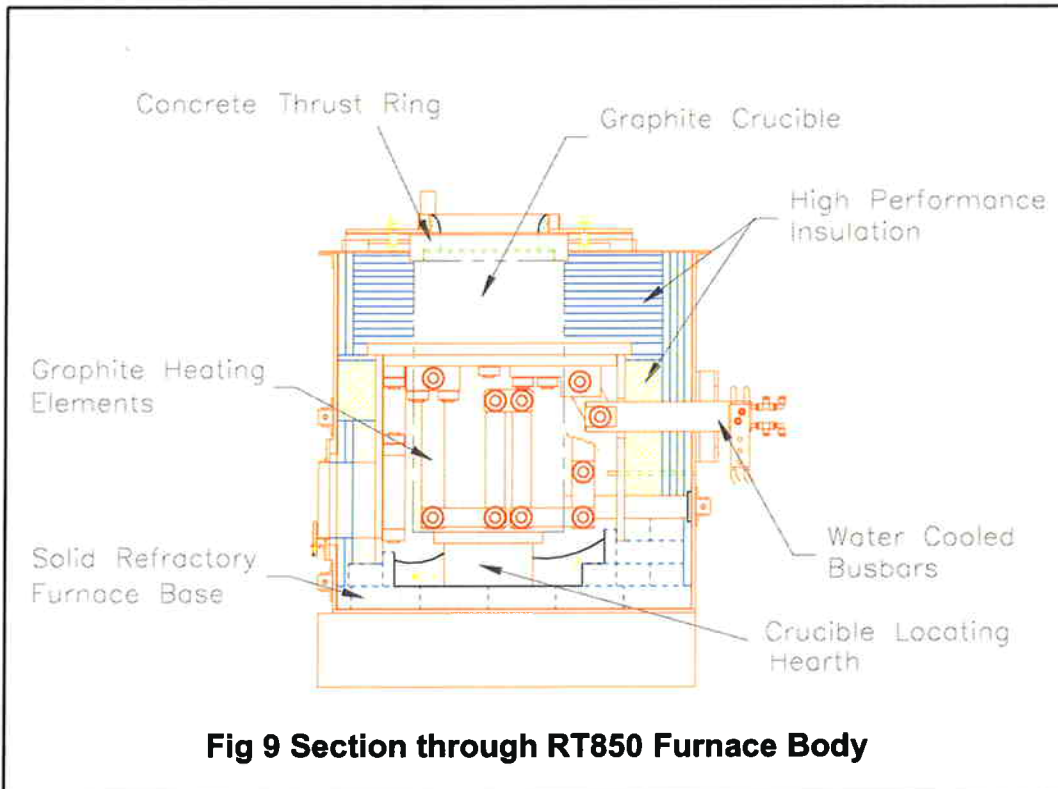

The furnace construction is shown in Fig 9 above.

Graphite bus bar and heating elements operating at an inherently safe low voltage provide the resistance heating. A 105 kVA air cooled transformer and thyristor complete the power pack.

The casting furnace is supplied with the following equipment: -

- a) Fume hood over the casting machine and side taphole. This is to be connected to a fume extraction system.

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead[®]

sales@rautomead.com
www.rautomead.com

b) Two rod strand withdrawals, each comprising a robust steel frame with two pairs of fully articulating shafts. The lower pair of shafts has a manual height adjustment whilst the clamping force is provided by pneumatic cylinders on the upper shafts. Drive to the withdrawal is by an AC servomotor with touchscreen controls, giving operator access to the withdrawal motion parameter settings.

c) Control cabinets housing furnace, withdrawal and fluidics instrumentation and controls utilising touch screen operator interfaces.

d) Platform tailored to each installation, but typically 7.5m x 5.1m x 1.95m high including access steps, handrails and kickboards

e) Primary Water cooling system comprising a dual pumps module (one operation, one standby) providing 15 m³/hr cooling water to the casting furnace. A plate cooler, sized to suit local ambient conditions, is used to cool the water. All mounted on a common skid complete with interconnecting pipework to furnace. Customer to supply cooling water to the heat exchanger, normally from standard atmospheric cooling tower system.

f) Secondary sparge cooling providing water spray cooling to the rod on exit from the casting dies. Comprises a stainless steel tank, circumferential water sprays, air wipes to contain the spray within the tank and collection tank with heat exchanger and recirculating pump.

g) Rod guides and run out tracks to suit sections sizes to be cast.



Fig 10 Rautomead Brass Rod Casting Installation. Note Fume extraction Hoods and hand Held Powered Bandsaw

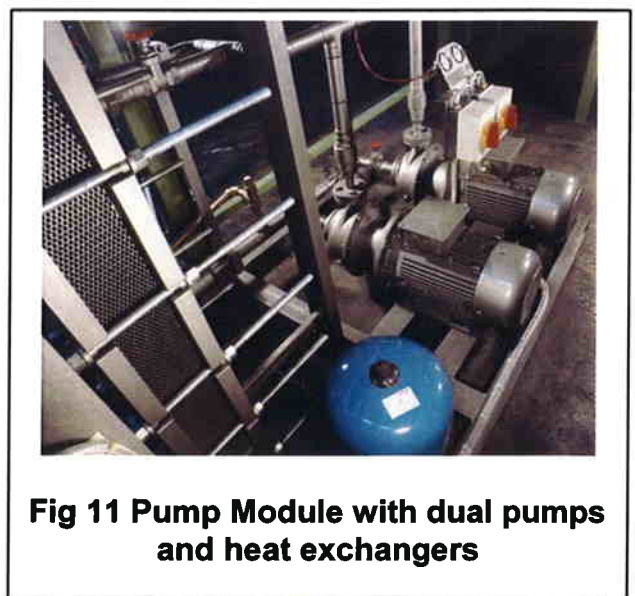


Fig 11 Pump Module with dual pumps and heat exchangers

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

rautomead

sales@rautomead.com
www.rautomead.com

5. Cut to Length

For the size range 15mm to 45 mm, a hand held electric powered bandsaw is suitable for cutting the strands during the casting process. Cut length is typically 3m to 4.0m.

6. Rod Pointing

The cut bars require one end to be turned down to the finished size to allow the bar to be entered into the shave bench dies. This is achieved using either a multi tool turning machine or a push type pointer.

Operation of these machines is manual. If several sizes are to be cast then the pointing is done on a batch basis. The furnace operator can often do this when not directly working on the casting furnace.

7. Hydraulic Shaving

A 30 tonne hydraulic shave bench capable of shaving up to 1mm depth over a maximum length of 4m. Approximately 15m overall length including a 3.5m loading table.

The loading table is designed to hold a 1 tonne bundle of rod, which is manually descrambled and loaded into the die assembly manually.



Fig 12 30 Tonne Hydraulic Shave Bench

The Manufacture of Semi Finished Brass Rod for Forging & Machining Applications

The die assembly comprises a guide die and two shave dies clad in an acoustic hood to minimise noise.

During operation the operator will push the pointed end of the rod through the shaving die assembly into the jaws and activate the shave cycle. The shave bench will shave the bar and eject into the collection trough with the jaws returning to the start point to accept the next rod.

An acoustic hood is provided over the machine to reduce noise from the shaving operation to acceptable levels.

8. Detagging Saw

Once shaving is complete the turned down “pointed end” must be removed and the bar cut to the desired length. This can be simply accomplished using a standard circular saw and length gauge. This is a manual operation again carried out in batches.

9. Bar Straightening

The process of casting followed by shaving may put a slight curve into the bars, which can cause difficulties if the bar is to be used in automatic feed machinery. The bars can be straightened using a standard two roll straightening machine.



Fig 13 Straightening Machine

10. Storage and Racking

If several sizes are manufactured and stored storage racking would be required. This is normally manufactured locally. Size of racking should allow for manual handling if single bars are to be moved or for forklift access, if bundles are to be handled.



Fig 14 Typical Storage Rack Arrangement for Brass Rod